

® = registered Trademark of Ciba Holding Inc.

# Tinuvin<sup>®</sup> 234

## Low Volatile Benzotriazole UV Absorber

### Characterization

Tinuvin 234 is a high molecular weight ultraviolet light absorber (UVA) of the hydroxyphenyl benzotriazole class, imparting excellent light stability to a variety of polymers.


### Chemical name

Phenol, 2-(2H-benzotriazol-2-yl)-4,6-bis(1-methyl-1-phenylethyl)

### CAS number

70321-86-7

### Chemical formula

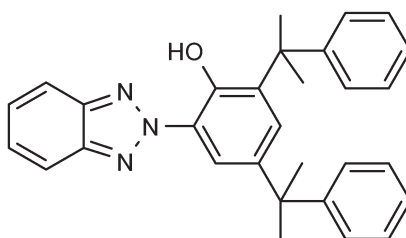

### Molecular weight

448 g/mol

### Applications

Tinuvin 234 is highly effective for polymers processed at high temperatures such as polycarbonates, polyalkylene terephthalates, polyacetals, polyamides, polyphenylene sulfide, polyphenylene oxide, aromatic copolymers, thermoplastic polyurethane and polyurethane fibers, as well as for polyvinylchloride, styrene homo- and copolymers. Applications include molded articles, films, sheets and fibers.

### Features/benefits

Tinuvin 234 features low volatility, exceptional light absorbing characteristics and good compatibility in various substrates. This makes the product particularly suitable for applications characterized by high surface area, such as films and fibers.

### Product forms

Tinuvin 234	Slightly yellow powder
Tinuvin 234 FF	Slightly yellow granules

### Guidelines for use

Use levels of Tinuvin 234 range between 0.15 and 0.60 %, depending on substrate and performance requirements of the final application. Tinuvin 234 can be used alone or in combination with other functional additives such as antioxidants (hindered phenols, phosphites) and HALS light stabilizers, where often a synergistic performance is observed. Extensive performance data of Tinuvin 234 alone or in combination with other additives are available in many of the substrates listed above.

**Physical Properties**

Melting Range	137–141 °C
Flashpoint	> 150 °C
Specific Gravity (20 °C)	1.22 g/ml
Vapor Pressure (20 °C)	~2 E-10 Pa


<b>Solubility (20 °C)</b>	<b>g/100 g solution</b>
Acetone	2
Chloroform	35
Cyclohexane	5
Ethanol	0.3
Ethyl acetate	4
n-Hexane	0.6
Methanol	<0.1
Methylene chloride	34
Toluene	20
Water	<0.01

**Volatility** (pure substance; TGA, heating rate 20 °C/min in air)

Weight Loss %	Temperature °C
1.0	264
2.0	280
5.0	302

**Absorbance spectrum**

(10 mg/l, Chloroform)

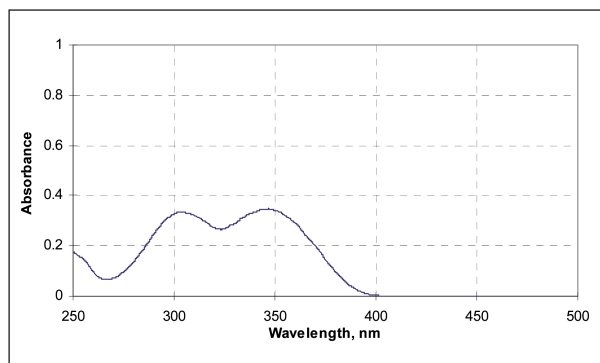

*Tinuin 234 exhibits high absorbance in the 300–400 nm region and minimal absorbance in the visible region (>400 nm) of the spectrum. The absorption maxima are at 302 nm and 343 nm ( $\epsilon = 16 \cdot 100 \text{ l/mol} \cdot \text{cm}$ ) in chloroform solution.*

**Handling & Safety**

Tinuin 234 exhibits a very low order of oral toxicity and does not present any abnormal problems in its handling or general use.

Detailed information on handling and any precautions to be observed in the use of the product(s) described in this leaflet can be found in our relevant health and safety information sheet.

**Note**

The descriptions, designs, data and information contained herein are presented in good faith, and are based on BASF's current knowledge and experience. They are provided for guidance only, and do not constitute the agreed contractual quality of the product or a part of BASF's terms and conditions of sale. Because many factors may affect processing or application/use of the product, BASF recommends that the reader carry out its own investigations and tests to determine the suitability of a product for its particular purpose prior to use. It is the responsibility of the recipient of product to ensure that any proprietary rights and existing laws and legislation are observed. No warranties of any kind, either expressed or implied, including, but not limited to, warranties of merchantability or fitness for a particular purpose, are made regarding products described or designs, data or information set forth herein, or that the products, descriptions, designs, data or information may be used without infringing the intellectual property rights of others. Any descriptions, designs, data and information given in this publication may change without prior information. The descriptions, designs, data and information furnished by BASF hereunder are given gratis and BASF assumes no obligation or liability for the descriptions, designs, data or information given or results obtained, all such being given and accepted at the reader's risk.

August 2010

